

## ASR related service life estimation for concrete pavements

 K. Seyfarth ,  C. Giebson,  H.M. Ludwig

Bauhaus-University, Coudraystr, (Weimar, Germany)  
: [katrin.seyfarth@uni-weimar.de](mailto:katrin.seyfarth@uni-weimar.de)

---

Received 26 October 2021  
Accepted 14 February 2022  
Available on line 10 May 2022

**ABSTRACT:** In a 5 years study on behalf of the German federal highway research institute (BAST), 71 pavement concretes from 53 highway sections across Germany were examined among other things regarding their residual potential for an alkali-silica reaction (ASR). An empirical approach could be derived for predicting the remaining service life of the concretes. By using earlier correlation data for the climate simulation concrete prism test (CS-CPT) compared to field performance, a translation of the testing period into service life was possible by using a fitted natural exponential function. In the result, the service life of all the pavement concretes could be estimated, ranging from 11 to 51 years, depending on the ASR potential of the concrete mixes with external alkali supply by NaCl de-icer solution. A first agreement between the prediction and the field performance could be found. Further monitoring is supposed to verify and improve the prediction.

**KEY WORDS:** Alkali-silica reaction; Concrete; Acceleration; Weathering; Cycles.

**Citation/Citar como:** Seyfarth, K.; Giebson, C.; Ludwig, H.M. (2022) ASR related service life estimation for concrete pavements. *Mater. Construcc.* 72 [346], e287. <https://doi.org/10.3989/mc.2022.15921>.

**RESUMEN:** *Estimación de la vida útil de los pavimentos de hormigón en relación con la RAS.* En un estudio de cinco años de duración encargado por el Instituto Federal de Investigación de Carreteras (BAST), se examinaron 71 hormigones de superficie de carreteras de 53 tramos de autopistas de toda Alemania para, entre otras cosas, determinar su potencial residual de reacción álcali-sílice (RAS). Se realizó un enfoque empírico para predecir la vida útil restante de los hormigones. Con este enfoque fue posible estimar la vida útil a partir de la prueba de simulación climática del prisma de hormigón (CS-CPT) comparando con el comportamiento en hormigones reales, utilizando una función exponencial natural ajustada. Como resultado, la duración de la vida útil de todos los hormigones de estos pavimentos podría estimarse entre 11 y 51 años, dependiendo de la potencial RAS de las mezclas de hormigón con aporte externo de álcalis por parte de los agentes de deshielo basados en NaCl. Se comprobó la concordancia entre la predicción y el comportamiento en la práctica; un mayor seguimiento en el tiempo verificará y mejorará esta predicción.

**PALABRAS CLAVE:** Reacción álcali-sílice; Hormigón; Aceleración; Intemperie; Ciclos.

**Copyright:** ©2022 CSIC. This is an open-access article distributed under the terms of the Creative Commons Attribution 4.0 International (CC BY 4.0) License.

## 1. INTRODUCTION

Concrete has been used successfully for a long time to build highway pavements in Germany. Concrete pavements meet highest requirements regarding durability, sustainability, load capacity, safety and economy and can provide many decades of service with little or low maintenance and repair. However, the use of concrete was increasingly questioned since the late 1990s because of a growing number of damage on pavements that had been caused or assisted by an ASR (Figure 1, Figure 2). A number of studies were launched in the following years to find out the reasons for the unexpectedly large number of ASR affected pavements. The main findings of these studies are briefly summarized below.

Certain slowly reactive aggregates, which do not need to be tested according to the German guideline for ASR (“Alkali-Guideline”) because it is allowed to classify them as non-reactive based on rock type and geographical origin, can still cause deleterious ASR in pavements (1). The former  $\text{Na}_2\text{O}$  threshold of 1.0 wt.% for pavement cements (CEM I) was not sufficiently low to avoid ASR damage with such aggregates safely (1). Slowly reactive aggregates tested with the German fog chamber test at 40 °C and classified as non-reactive can still cause deleterious ASR in pavements (2-5). In concrete with alkali reactive aggregates, ASR can be triggered and accelerated highly by an external application of NaCl de-icers (1-16). The mechanism is based on an increase of the silica dissolution in presence of NaCl. The formation of Friedel’s salt, assumed earlier to increase the NaOH concentration in the concrete pore solution, turned out to be a side effect that is not required for ASR and does not result in an increase of the pH (4, 12, 13, 16). In concrete with alkali reactive aggregates and exposed to external alkalis, low alkali Portland cements (CEM I) can delay but not prevent a deleterious ASR (4, 6, 12, 13). The two mortar-bar tests, introduced in 2007 in Germany, are unable to identify reliably if aggregates are suffi-

ciently non-reactive for use in concrete pavements (4, 5). ASR performance-tests as the climate simulation concrete prism test (CS-CPT) are appropriate to assess the ASR potential of pavement concrete job mixes (2-11, 13, 14). Microcracks in concrete induced by traffic loads promote the ingress of water and NaCl solution what further accelerates the ASR in concrete with alkali reactive aggregates (5, 14, 15).

In 2010 and 2011, the federal highway research institute (BAST) launched a large-scale survey on concrete pavements. That is around 5,800 km of German highways. The scope of the project was to obtain reliable information about the extent of ASR affected and suspected pavements. The result was that more than 1,500 km were more or less affected by an ASR, i.e. more than 25 %. Based on these results, the BAST starts a large research program in 2012 to clarify the reasons for the damage and to derive measures to safely avoid further damage to concrete pavements.

As a joint research group, the Bauhaus-University Weimar, the Ruhr-University Bochum and the Federal Institute for Materials Research and Testing were assigned with that task. In the following 5 years, a selection of 53 highway sections across Germany (Figure 2) were sampled, diagnosed and tested in many different ways. Additionally, all available data about the highway sections and concrete compositions were investigated and linked to the laboratory results. The present paper focuses on the developed method to estimate the ASR-related service life for concrete pavements.

## 2. MATERIALS AND METHODS

### 2.1. Selection and sampling of the highway sections

Overall, 53 highway sections across Germany were selected for the sampling (Figure 2, left). The



FIGURE 1. Example of an ASR-damaged highway pavement section with typical crack pattern and discolorations around the joints, especially at the cross points.



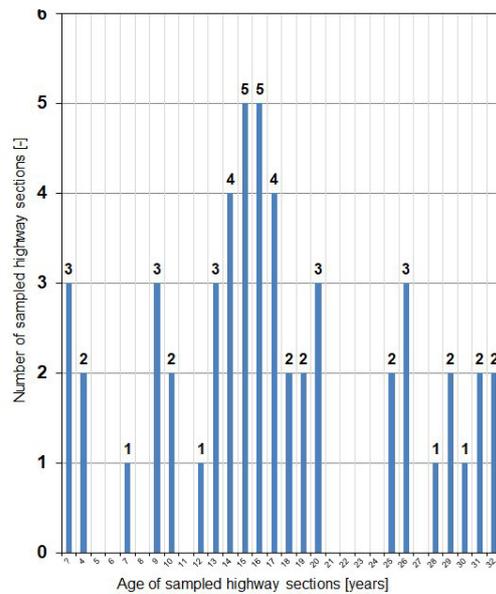


FIGURE 2. Locations (left) and age at the time of sampling (right) for the 53 sampled highway sections across Germany.

selection was based on different criteria as visible signs for an ASR, service life, type of construction and used aggregates, i.e. the sections were not chosen randomly. For verification, 3 sections that were built after the introduction of the new advisory circular for concrete pavements in 2005 were sampled (17). Until now, no damage could be detected on those sections. In total, 105 individual parameters as year and type of construction, type, origin and properties of the concrete raw materials, traffic load data, geographic characteristics, weather conditions during the placing and many more were tried to be collected for every section. However, for nearly 30 % of the sampled highway sections only limited or no data at all were available.

Among the 53 selected highway sections, 33 were built single-layered and 20 dual-layered with different concrete compositions in each layer. In total 71 different concrete compositions had to be investigat-

ed. About 15 cores of different diameter (Ø 100, 150 and 350 mm) were extracted from each section for different investigations. For the residual expansion measurements, 3 cores of Ø 150 mm were extracted from the single-layered pavements, each one from the centre of a truck lane slab. In case of the dual-layered pavements, 3 cores of Ø 350 mm were extracted, each one from the centre of a shoulder slab to prevent the traffic lane from damage (Figure 3).

### 2.2. Climate simulation concrete prism test

Residual expansion measurements were performed with the climate simulation concrete prism test (CS-CPT). The CS-CPT was developed at the Bauhaus-University Weimar to test specific concrete compositions (job mixtures) for their ASR potential with the option to take external alkalis into consid-



FIGURE 3. Sampling of a large (Ø 350 mm) core from a shoulder slab.

eration (3-7, 9, 14, 18, 19). Usually, concrete prisms (100×100×400 mm<sup>3</sup>) are cast, applied with a test solution (water, de-icer solutions etc.) and subjected to cycles of alternating temperature and moisture conditions.

One cycle runs for 21 days and consists essentially of 4 days of drying at 60 °C and ≤ 10 % relative humidity (RH), 14 days of wetting at 45 °C and 100 % RH and finally 3 days of freeze-thaw-cycling between +20 °C and -20 °C (Figure 4, left, Figure 5). Besides 3 initial sub-cycles between 5 °C and 65 °C within 12 hours, 3 more sub-cycles between +10 °C and -10 °C within 12 hours are done prior to the 6 freeze-thaw cycles in order to simulate rapid temperature changes that cause stresses in the prisms. The cycling is automated within a walk-in climate simulation chamber for a period of usually 9 months or 12 cycles (Figure 4, right). After every cycle the expansion and mass of the prisms are recorded.

Since prisms of the regular size could not be obtained from the highway sections, two alternative

kinds of samples were prepared after a pre-storage of the cores at 20 °C and 65 % RH for about 6-8 weeks. For the single layered pavements, 3 cores (Ø 150 mm, l ≥ 250 mm) per section were cut lengthwise into halves and each 3 of them were exposed to water (control) and NaCl solution respectively (Figure 6, left). In case of the dual-layered pavements, 3 cores (Ø 350 mm, l ≥ 250 mm) per section were prepared in a way that 4 prisms (100×100×300 mm<sup>3</sup>) could be obtained, each 2 representing the top and bottom layer concrete (Figure 6, right). In total 12 prisms were obtained for the dual-layered pavements, each 6 representing the top and bottom layer concrete with 3 prisms each exposed to water (control) and NaCl solution respectively. In every sample 2 stainless steel studs are embedded for expansion measurements and a flexible foam rubber tape is glued around the edges of the upper side to form a guard that will retain the applied test solution later on.

At the end of the first drying phase the initial length and mass of the samples are measured at


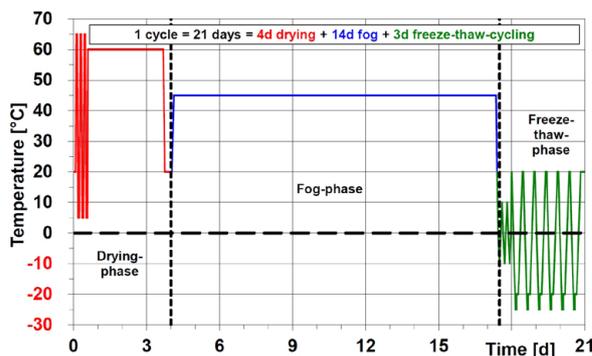


FIGURE 4. Temperature scheme of the CS-CPT (left) and open chamber with prisms (right).

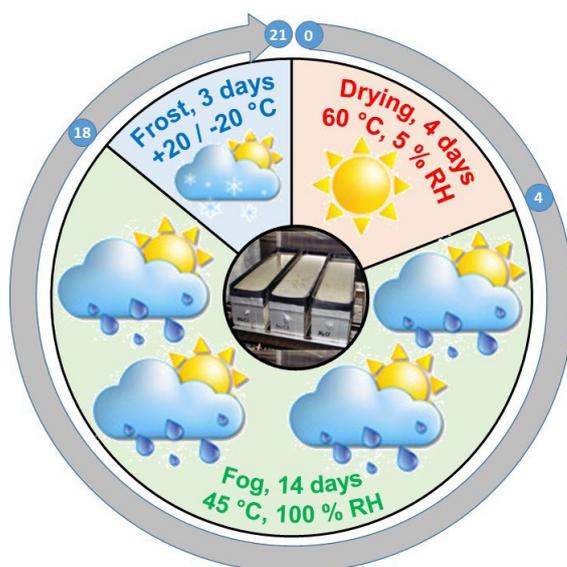

Day	Action
0	<b>Start of the cycle</b> Begin of the <b>drying phase</b>
4	Zero readings for expansion and mass of the prisms (only after 1 <sup>st</sup> drying phase, i.e. once in the 1 <sup>st</sup> cycle) Application of water (reference) and/or de-icing solutions onto the prisms Begin of the <b>fog phase</b>
18	Transition into the <b>frost phase</b> (6 freeze/thaw cycles)
21	<b>End of the cycle</b> Readings for expansion and mass
0	<b>Start of the next cycle</b>

FIGURE 5. Schematic diagram of the 3 phases of a climate simulation cycle (12 cycles are required to evaluate the suitability of pavement concrete compositions with the CS-CPT).

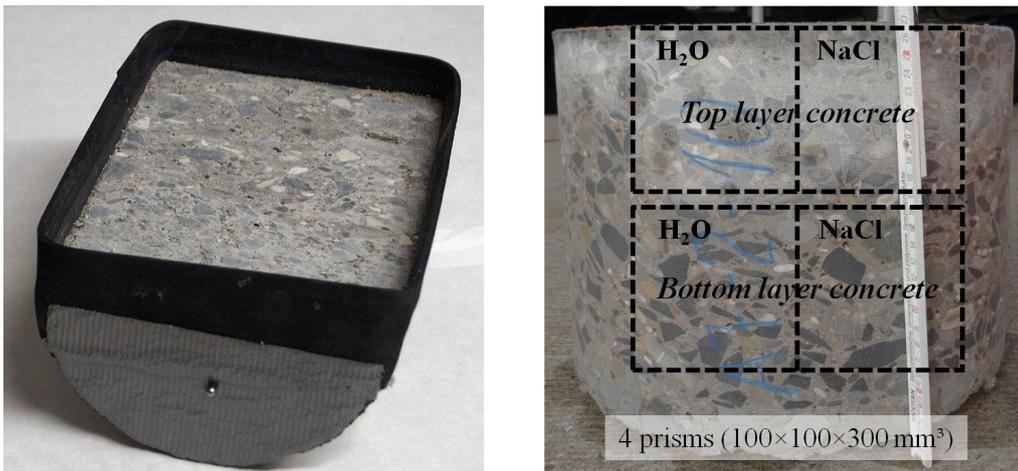


FIGURE 6. Samples for the CS-CPT, Ø 150 mm core half for single-layered pavements (left) and scheme for obtaining 4 prisms (100×100×300 mm<sup>3</sup>) from a Ø 350 mm core for dual-layered pavements (right).

20 °C and 300-450 g (depending on the surface area of the samples) of the test solution is applied to each sample for the first time. The test solution remains on the samples until the end of the cycle. After the cycle, the test solution is removed to measure length and mass of the samples at 20 °C and is replaced once the readings are obtained. During the second drying phase, the test solution evaporates, leaving behind dissolved substances as NaCl from the applied NaCl de-icer solution. At the end of the second drying phase new test solution is applied again on each prism. This process is repeated until 10 cycles for the highway samples and 12 cycles for laboratory concrete samples are completed. The NaCl de-icer solution was prepared at a concentration of 0.6 mol/l based on earlier studies (2, 4). With some assumptions, the amount of NaCl that is applied within 8 cycles (about 2800 g/m<sup>2</sup>) corresponds to nearly the average amount of NaCl that is applied during one winter period in the field on German highways. The standard expansion limits are 0.4 mm/m for application of water (control) and 0.5 mm/m for application of de-icer solutions. The additional 0.1 mm/m in case of the de-icer solution treatment is due to an allowance for the higher expansion of the prisms caused by hygroscopically absorbed water. For residual expansion measurements, however, the limits are 0.6 mm/m for application of water (control) and 0.7 mm/m for application of de-icer solutions, adopted from (20).

### 3. RESULTS AND DISCUSSION

The expansions for the samples exposed to NaCl solution during the CS-CPT range between 0.21 and 3.45 mm/m, representing very different ASR potentials from very low to very high (Figure 7). The expansions for the samples exposed to water (results

not presented) are significantly lower, confirming the strong influence of externally applied alkalis in promoting ASR as reported earlier (2-4, 8, 13, 18). In addition, the results for the samples exposed to water turned out to be helpful in identifying other durability issues as frost damage or delayed ettringite formation. This paper is focused on ASR for what in the following, the results for the samples exposed to NaCl solution are further analysed.

A major difficulty emanates from the different age of the concretes. A conventional evaluation of the results by assessing the expansions after a fixed testing period would not allow comparing the different concretes directly to each other or to estimate their remaining service life. Hence, an evaluation that considers the age of the concretes, which ranges between 4 to 32 years, was required.

Based on an earlier correlation between the CS-CPT and field performance (8, 11, 18), the testing period until reaching the acceptance limit (0.5 mm/m for lab concrete samples, 0.7 mm/m for field concrete samples) and the time when first damage (cracks) ap-

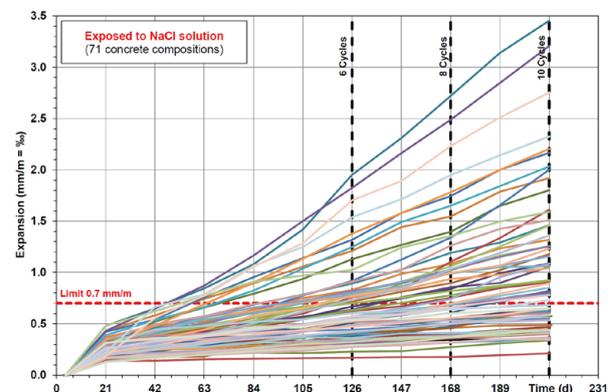


FIGURE 7. Expansions during the CS-CPT for the 71 different concrete compositions exposed to NaCl solution.

peared in the field was plotted against each other. This could be done, however, for a very limited number (only 2) of concretes only because both field data as well as corresponding testing results were required. Another issue is the determination of the point in time when first damage appeared in the field which can be done only very roughly. Also, the pavements still can be in service for several years beyond this point, so it does not necessarily represent the end of its service life. Nevertheless, the available data were used for a first regression analysis together with the following 3 boundary conditions (Figure 8):

1. The 0/0 criteria, which defines the starting point.
2. The need for a testing period of 12 cycles to evaluate new pavement concretes for the intended service life (in Germany) of about 30 years (before construction).
3. And the observation in the field that the ASR in pavements often follows an exponential function, i.e. the pavements show no damage for many (8-12) years but often have to be replaced a few (2-5) years after the first damage appeared.

The function that fits best to the data points and boundary conditions are shown in Figure 8 and was used in the project to convert the period of testing

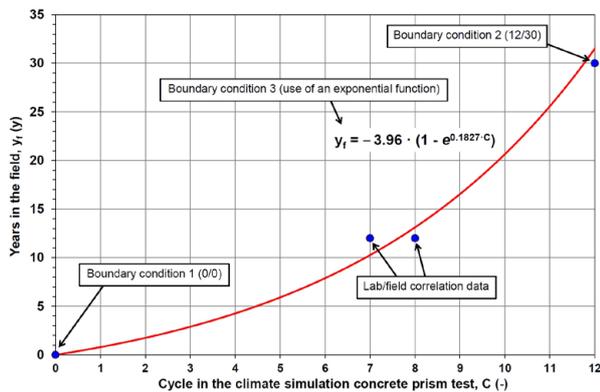


FIGURE 8. Exponential function for converting the cycles of the CS-CPT into an equivalent number of years in the field.

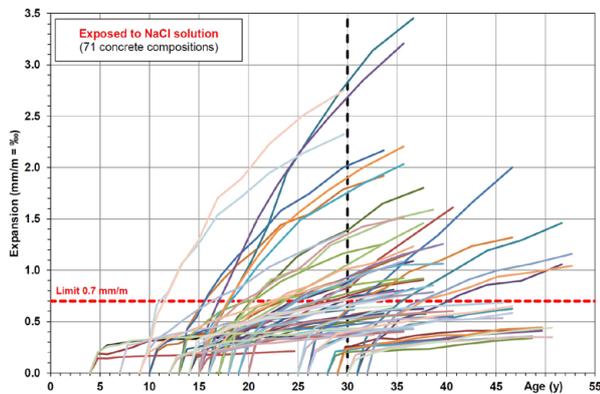


FIGURE 9. Expansions during the CS-CPT for the 71 different concrete compositions exposed to NaCl solution and considering the age of the concretes.

into a corresponding time in the field (Figure 9). By using the data from Figure 9, the service life could be estimated for every concrete individually. For example, a pavement built in 2004 (Figure 10) and 9 years old at the time of sampling shows a considerable expansion exceeding the limit after about 11 years, what would be around 2015. In fact, this highway section was replaced in 2016.

The estimated service lives range between 11 to 51 years (Figure 11). In Figure 11, the start of the bars indicate the year of construction for the respective sections and its ends represent either:

- Red bars: the approximate year ASR damage is expected before 30 years of service, based on the concrete expansion exceeding the limit in the CS-CPT before 30 years (Figure 9).
- Green bars: the approximate year no ASR damage is expected for at least 30 years, but maybe later, based on the concrete expansion not exceeding the limit in the CS-CPT before 30 years (Figure 9).
- Grey bars: the approximate year no ASR damage is expected based on the concrete expansion not exceeding the limit in the CS-CPT (Figure 9), but the testing period (10 cycles) was too short to test for a full 30 year service life.

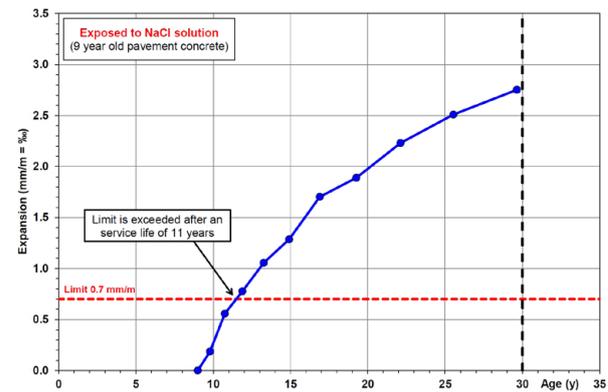


FIGURE 10. Expansion for a single-layer concrete (9 years old at the time of sampling) after converting the testing period of the CS-CPT into years in the field.

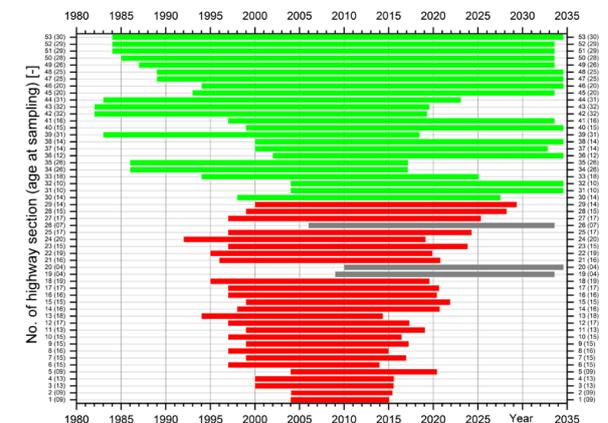


FIGURE 11. Estimated service lives (given years in the bars) for all 53 sampled highway sections.

In total, 51 % of the sampled highway sections would reach a service life of at least 30 years without ASR damage (Figure 12). For the dual-layered highway sections, the respective higher expansion from either the top or bottom layer concrete was used. Some of those sections were around 30 years old at the time of sampling and without any ASR damage. Consistently, only low residual expansions were measured in these cases and high residual service lives were obtained. Since the CS-CPT was stopped after 10 cycles (for samples from existing highways), the estimation was restricted to a period of about 20 years. In many cases, however, the low expansions suggest an even longer service life without ASR damage. In some other cases, the expansions exceed the limit after 30 years, indicating a low but acceptable ASR risk. For the three younger highway sections built after 2005, the testing period was too short for an estimation of 30 years. However, the low residual expansions suggest that they will reach at least 30 years without showing ASR damage.

On the other hand, the results indicate that for 49 % of the sampled highway sections ASR damage is likely to occur before an age of 30 years (Figure 12). For some of them, ASR damage can be expected after about 11 years only. Those sections were built exclusively between 1990 and 2004, i.e. prior to the introduction of the advisory circular for pavements in 2005 and the availability of better test methods as the CS-CPT. For all the sections built before 1990 and still in good condition, the expansions nicely confirm a sufficiently low ASR potential. However, this does not mean in general that sections built before 1990 had no ASR issues at all, because there is no doubt that ASR affected sections from that time had to be replaced long ago and were not available anymore for the sampling.

It is important to note that the estimation assumes that the service life ends after the limit of 0.7 mm/m has been exceeded in the CS-CPT. However, this is a simplification and not necessarily true because it

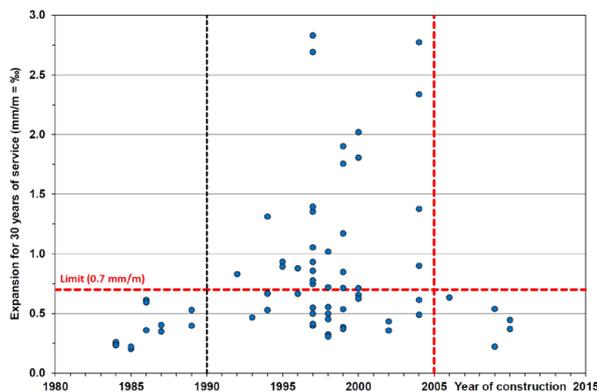


FIGURE 12. Comparison of year of construction and 30-year expansion exposed to NaCl solution for all sampled highway sections (sections  $\geq 30$  years old not included, in case of dual-layered highway sections, top and bottom concrete separately).

is unknown so far what exactly happens in the field to the pavement at the time the expansion limit is exceeded in the laboratory. Hence, at this point it is obvious that the actual service life will fluctuate several years around the calculated year. Also, every concrete composition is likely to have its very own conversion function, which depends on the alkali-reactivity of the aggregates, the alkali content, the type of the binder and the exposure conditions (temperature, moisture, external alkalis etc.). Hence, the derived conversion function allows a very first, average conversion of the CS-CPT testing period into a corresponding lapse of time in the field, valid for pavement concretes with slowly reactive aggregates and exposed to externally applied NaCl. It is provided as a very first tool for better planning maintenance and repair measures in the field. A further monitoring of the sampled highway sections would help to verify the predictions and to refine the approach in the future.

#### 4. CONCLUSIONS

In a 5 year study on behalf of the German federal highway research institute (BAST), 71 pavement concretes (top and bottom concrete samples) from 53 highway sections across Germany were extensively examined and tested regarding their residual ASR potential.

For an ASR related service life estimation of the sampled sections, an empirical approach for converting the period of testing into a corresponding lapse of time in the field was derived based on a natural exponential function. In the result, about 50 % of the sampled sections already have reached or are very likely to reach a 30 year service life without ASR damage. About another 50 %, however, are suspected to show ASR damage prior to a 30 year service life.

For highway sections built after 2005, a sufficiently low ASR potential was found. This confirms the effectiveness of the new regulations for preventing ASR in highway pavement concrete (ARS 04/2013) in Germany, introduced in 2005.

In an ongoing research project with BAST (No. 08.0247/2016/GRB), the 53 highway sections investigated in this study are currently further monitored. First results for some of the highway sections show a good agreement between the estimated service life and the performance in the field. The new data will help to verify and further improve the approach. The derived service life estimation for highway pavement concretes is provided as a tool for better planning and conducting maintenance and repair measures in the field. With the current state of knowledge and a consistent application of the CS-CPT, ASR damage can be reliably avoided when building new concrete highways.

## ACKNOWLEDGEMENTS

The authors gratefully acknowledge the financial support of the Federal Ministry of Transport and Digital Infrastructure (BMVI) and the BAST and the fruitful collaboration with the project partners. This report is based on the research project carried out at the request of the Federal Ministry of Transport and Digital Infrastructure, represented by Federal Highway Research Institute, under research project No. 08.2014/2011/LRB and 08.0247/2016/GRB.

The authors are solely responsible for the content.

## AUTHOR CONTRIBUTIONS:

Conceptualization: K. Seyfarth, C. Giebson. Data curation: K. Seyfarth, C. Giebson. Formal analysis: C. Giebson. Investigation: K. Seyfarth, C. Giebson. Methodology: K. Seyfarth, C. Giebson. Project administration: H.M. Ludwig. Resources: H.M. Ludwig. Supervision: H.M. Ludwig. Validation: K. Seyfarth, C. Giebson. Visualization: C. Giebson. Writing, original draft: K. Seyfarth, C. Giebson.

## REFERENCES

- Öttl, C. (2004) Die schädigende Alkalireaktion von gebrochener Oberrhein-Gesteinskörnung im Beton. PhD thesis, Otto-Graf-Institut, Universität Stuttgart. <https://doi.org/10.18419/opus-5969>.
- Seyfarth, K.; Giebson, C. (2005) Beurteilung des AKR-Schädigungspotentials von Betonen mittels Klimawechsellagerung. *Beton-Stahlbetonbau*. 100,189-192. <https://doi.org/10.1002/best.200590271>.
- Stark, J.; Giebson, C. (2006) Assessing the durability of concrete regarding ASR. In: Malhotra, V.M. (ed.): *Proc 7th CANMET/ACI International Conference on Durability of Concrete*, Montreal, Canada, pp. 225-238.
- Giebson, C. (2013) Die Alkali-Kieselsäure-Reaktion in Beton für Fahrbahndecken und Flugbetriebsflächen unter Einwirkung alkalihaltiger Enteisungsmittel. PhD thesis, Bauhaus-Universität Weimar.
- Giebson, C.; Volland, K.; Ludwig, H.M.; Meng, B. (2015) Untersuchungen zur alkali-kieselsäure-reaktion in vorgeschädigten fahrbahndeckenbetonen. *Beton Stahlbeton*. 110, 13-21. <https://doi.org/10.1002/best.201400094>.
- Stark, J., Seyfarth, K. (2006) Performance testing method for durability of concrete using climate simulation. In: Malhotra VM (ed) *Proc 7th CANMET/ACI International Conference on Durability of Concrete*, Montreal, Canada, pp. 305-326.
- Stark, J.; Seyfarth, K. (2008) Assessment of specific pavement concrete mixtures by using an ASR performance-test. In: Broekmans MATM, Wigum BJ (eds) *Proc 13th ICAAR*, Trondheim, Norway, pp. 320-329.
- Seyfarth, K.; Giebson, C.; Stark, J. (2009) Prevention of deleterious ASR by assessing aggregates and specific concrete mixtures. In: Tasnimi AA (ed) *Proc 3rd International Conference on Concrete and Development*, Tehran, Iran, pp. 159-169.
- Seyfarth, K. (2010) ASR diagnosis in concrete cores from highway pavements. RILEM TC 219-ACS Seminar: Recent Developments in AAR, Ponta Delgada, Azores/Portugal.
- Stark, J.; Freyburg, E.; Seyfarth, K.; Giebson, C.; Erfurt, D. (2010) 70 Years of ASR with no end in sight? (Part 2). *ZKG International*. 5, 55-70.
- Giebson, C.; Seyfarth, K.; Ludwig, H.M. (2012) Correlation of ASR performance testing for highway pavement concretes with field performance and investigations into boosting the alkali level. In: Drimalas T, Ideker JH, Fournier B (eds) *Proc 14th ICAAR*, Austin, Texas, USA.
- Heisig, A.; Urbonas, L.; Beddoe, R.E.; Heinz, D. (2016) Ingress of NaCl in concrete with alkali reactive aggregate: effect on silicon solubility. *Mater. Struct.* 49, 4291-4303.
- Giebson, C.; Seyfarth, K.; Ludwig, H.M. (2016) Influence of sodium chloride on ASR in highway pavement concrete. In: Bernardes H, Hasparyk NP (eds) *Proc 15th ICAAR*, São Paulo (Brazil).
- Giebson, C.; Volland, K.; Ludwig, H-M.; Meng, B. (2017) Alkali-silica reaction performance testing of concrete considering external alkalis and preexisting microcracks. *Struct. Concr.* 18 [4], 528-538. <https://doi.org/10.1002/suco.201600173>.
- Wiedmann, A.; Weise, F.; Kotan, E.; Müller, H.S.; Meng, B. (2017) Effects of fatigue loading and alkali-silica reaction on the mechanical behavior of pavement concrete. *Struct. Concr.* 18 [4], 539-549. <https://doi.org/10.1002/suco.201600179>.
- Giebson, C.; Seyfarth, K.; Ludwig, H.M. (2021) Aggregate dissolution kinetics. In: Batista AL, Santos Silva A, Fernandes I, Oliveira Santos L, Custódio J, Serra C (eds.): *Proc 16th ICAAR*, Vol. 1, Lisboa, Portugal, 161-173.
- Bundesministerium für Verkehr, Bau- und Stadtentwicklung (2013) Allgemeines Rundschreiben Straßenbau Nr. 04/2013, Betreff Vermeidung von Schäden an Fahrbahndecken aus Beton in Folge von Alkali-Kieselsäure-Reaktion (AKR).
- Sims, I.; Poole, A.B. (2017) Alkali-aggregate reaction in concrete: A world review. *CRC Press/ Balkema*, London.
- FGSV (AG Betonbauweisen): *TP B-StB – Teil 1.1.10, AKR-Potenzial und Dauerhaftigkeit von Beton (Klimawechsellagerung)*. Ausgabe 2018.
- Deutscher Ausschuss für Stahlbeton (Hrsg.) Empfehlung für die Schadensdiagnose und Instandsetzung von Betonbauwerken, die infolge einer Alkali-Kieselsäure-Reaktion geschädigt sind. Ausgabe 2002.